

## XYPEX CRYSTALLINE CRACK REPAIR

### TYPE 1 - Full Crack Repair, Leaking (Minor Crack and Cold Joints)

2018-09

The information presented is in addition to Xypex product data sheets and is not meant to replace these or any other installation guides but rather is meant to give a general description of the installation practices and procedures surrounding the use of Xypex products for waterproofing and protecting concrete and while normally provide an acceptable final appearance they are not meant as aesthetic finishes. Refer to Safety Data Sheets for safety information, applicators need to use all products and equipment in line with manufacturers and industry requirements.

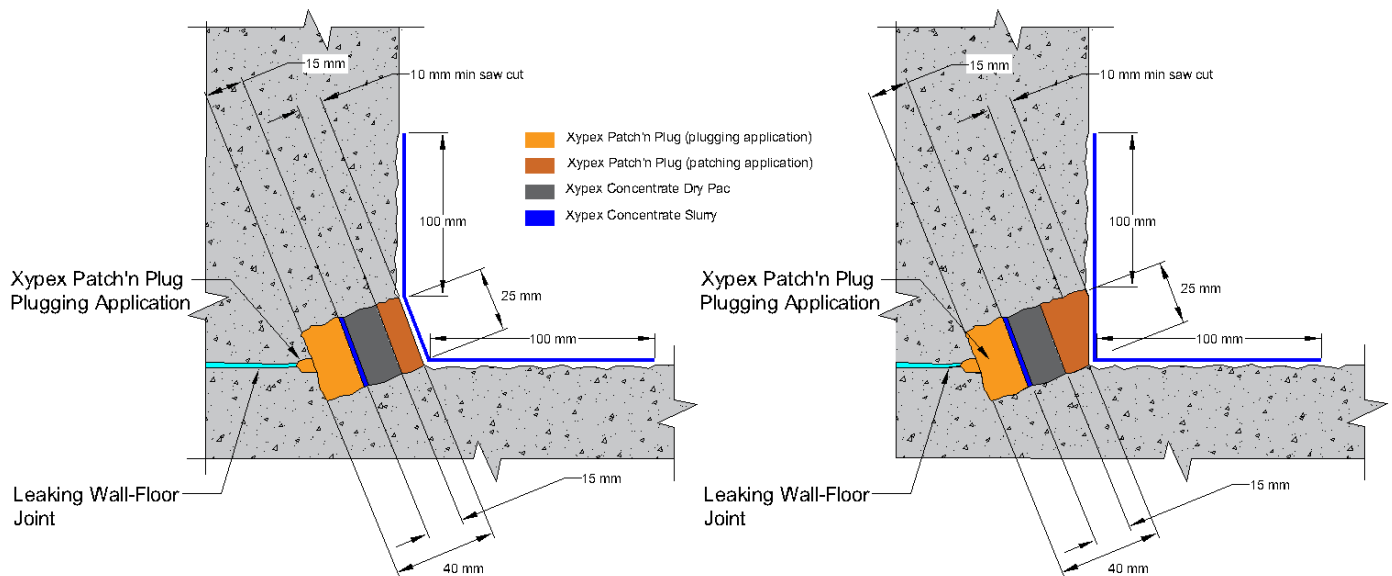


Figure 2, Details of the leaking wall-floor joint repair/cold joint (Schematic)

#### B. ACTIVE LEAKING WALL-FLOOR JOINT

##### ROUTING

- Form a dovetail or rectangular shaped rout (A "V" shaped rout is not acceptable) along the entire length of the crack or faulty construction joint with a dimension of approximately 25 mm of width and 40 mm of depth as follows: *Saw cut the perimeter to the whole depth of 40 mm. Remove the concrete from the rout using a jackhammer (pneumatic, electro-mechanical or hydraulic). Remove all the loose and unsound materials. Care is to be taken to avoid damage to the sound concrete adjacent/below the repair. Roughen edges of the rout to a CSP-3 minimum profile. Recommend diamond based masonry with soft matrix blade for rough finish.*
- Clean the rout including 100 mm of concrete surface from each side of the rout using high pressure water blasting (approx. 3500 – 5000 psi or as required) to remove all the dirt, debris and loose particles and saturate the substrate. Conduct test wash prior to full application. Ensure surface is rough with a surface profile CSP-5 to International Guidelines, refer to Surface Profile Chips.

##### PLUGGING LEAK/CRACK

- For localised/high flows, conduct plugging by mixing Patch'n Plug three and a half (3.5) parts dry powder to one (1) part clean water by volume into stiff putty. DO NOT add more water. Form plug with gloved hand. For

## XYPEX CRYSTALLINE CRACK REPAIR

### TYPE 1 - Full Crack Repair, Leaking (Minor Crack and Cold Joints)

2018-06

leaking cracks, begin at the point of lowest water flow and work towards the point of greatest water flow. Place plug into the cracked/leaking cavity firmly until the plug is hard and continue application into the crack/leak until the water flow has diminished. Where there is high volume water flow or high hydrostatic pressure a bleeder hose may be necessary to relieve the water pressure while sealing the crack/leak. Refer to data sheet for bleeder hose applications.

#### PLUGGING LAYER

- Mix three and a half (3.5) parts *Xypex Patch'n Plug* to one (1) part clean water (by volume) into stiff putty. DO NOT add more water. Form into plugs by rolling the putty in gloved hands with approximate length of 100 mm and diameter of 25 mm.
- Ensure concrete is saturated and absorbed by concrete then remove excess water to achieve a saturated surface dry (SSD) state. Compress the hardened *Xypex Patch'n Plug* plugs into the base of the whole length of the rout using a hammer and a block until the water flow stops. The approximate thickness of plugging application must be maximum 15 mm.

**NOTE:** Conduct test application of *Xypex Patch'n Plug*. *Xypex Patch'n Plug* is a very rapid setting product. Project conditions may require variation of mixing to 3.25 parts powder to 1 part water by volume. Water temperature should be 15°C - 20°C. Test application to ensure adequate finish and mixing ratios are compatible with project conditions.

#### CONCENTRATE SLURRY

- Mix five (5) parts *Xypex Concentrate* dry powder to two (2) parts clean water by volume into slurry consistency. Allow mix to stand and start to harden, then reagituate. Apply *Xypex Concentrate* slurry coat over the *Xypex Patch'n Plug* using a semi-stiff nylon bristle brush. Coating must be uniformly applied with a nominal thickness of 1.25 mm (0.65 - 0.8 kg/m<sup>2</sup>).
- Allow the *Xypex Concentrate* slurry coat to reach initial set.

#### DRY PAC LAYER

- Mix six (6) parts *Xypex Concentrate* dry powder to one (1) part clean water by volume as Dry Pac. Lumps should be present in mix. Compress very firmly over the entire rout surface with a hammer and block or use pneumatic packing device to fill an approximate depth of 15 mm.
- Remove any loose material from the rout using a semi-stiff nylon bristle brush and ensure required thickness of *Xypex Patch'n Plug* can be applied. Clean edges of the rout. Apply a fine mist spray of clean water to seal the Dry Pac surface.

#### PATCHING LAYER

- Mix four (4) parts *Xypex Patch'n Plug* dry powder to one and a half (1.5) parts clean water by volume to a workable mortar consistency. Apply *Xypex Patch'n Plug* as scrub coat and patching application over the Dry Pac to fill rest of the rout with CSP-3 (brush finish) (approximately 10 mm). Allow a minimum of 1 hour to set.

**NOTE:** Conduct test application of *Xypex Patch'n Plug*. *Xypex Patch'n Plug* is a very rapid setting product. Project conditions may require variation of mixing to 3.25 parts powder to 1 part water by volume. Water temperature should be 15°C - 20°C. Test application to ensure adequate finish and mixing ratios are compatible with project conditions.

#### CONCENTRATE FINAL COATING

- Ensure that the repaired zone including 100 mm of concrete surface from each side of the repaired rout is saturated surface dry (SSD) condition. If the surface dries out after initial water application, it must be re-wetted using a fine mist spray of clean water. Remove any excess surface water so no glistening water present.

**NOTE:** Do not use high pressure water blasting for re-wetting of repaired zone and surrounding concrete surface. High pressure water blasting may cause damage to the repaired area.

- Mix as per point 6, and apply nominal 1.25 mm *Xypex Concentrate* slurry (0.65 - 0.8 kg/m<sup>2</sup>) over the repaired area covering 100 mm width of both wall and floor sides. Start curing of *Xypex Concentrate* coating as soon as the coating has set to the point where it will not be damaged

## XYPEX CRYSTALLINE CRACK REPAIR

### TYPE 1 - Full Crack Repair, Leaking (Minor Crack and Cold Joints)

2018-09

by a fine mist spray of clean water (about 2-4 hours after application depending on the weather conditions). Cure the applied coating with a fine mist spray of clean water at least 3 times a day for 2-3 days.

#### NOTE:

- For joints requiring early trafficable/hydrostatic pressure. Contact the Xypex Technical Department for possible alternatives.
- For joints where *Xypex Patch'n Plug* plugs do not 'hold'. A bleeder hose may require installation. Contact your Xypex Representative or the Xypex Technical Department for bleeder requirements
- For joints subject to movement (construction joints, expansion joints, contraction joints, isolation joints) contact a Xypex Representative or Xypex Technical Department for possible alternatives.
- Information presented is in addition to Xypex Data Sheets and is not meant to replace these or any other information surrounding the use of Xypex Products.
- This joint method, while normally provides an acceptable final appearance, is not meant for aesthetic finishes.
- Refer to Xypex Concentrate Method Statement for application requirements for paints, epoxies, grout, cement parge coat, plaster, tiles, stucco or similiar products.
- Refer to Safety Data Sheet for safe application requirements.